



METHOD STATEMENT

SIKAFLOOR[®]-263 SL HC – 2 MM

SELF-SMOOTHING

SIKA LIMITED (VIETNAM)

CLASSIFICATION

BUILDING TRUST




1 SCOPE

- Self-smoothing system for concrete and cement screed with normal up to medium heavy wear e.g. storage and assembly halls, maintenance workshops, garages, logistic and sales area.

2 ADVANTAGES

- High wear resistance
- Good chemical resistance
- High Safety
- Aesthetic and surface texture
- Comfort and care

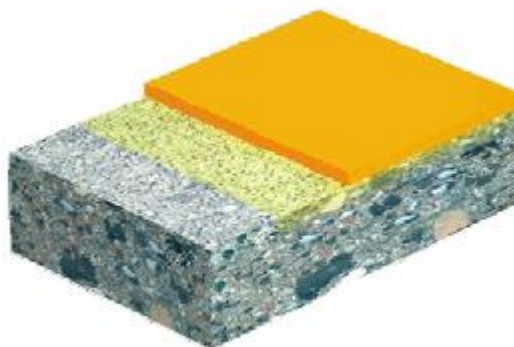

3 SIKAFLOOR®-263 SL HC – 2 MM - SYSTEM

DETAILS	COATING SYSTEM	PRODUCT	CONSUMPTION
Primer			
Normal substrate / Porous substrate	Primer	Sikafloor®-161 HC	0.3 - 0.5 kg/m ²
If needed, moisture barrier (if > 4% pbw moisture content into the substrate)			
Epocem Primer	Primer	Sikafloor® Repair Epocem Module	Approx. 0.15 Kg/m ²
Moisture barrier	Body coat	Sikafloor®-81 Epocem New HC(2 mm mini)	2.1 kg/m ² /mm
Self smoothing			
Wearing course, 2 mm	Self Smoothing	Sikafloor®-263 SL HC + Quartz sand (0.1 - 0.3 mm)	Approx. 1.9 kg/m ² binder + 1.9 kg/m ² quartz sand for 2 mm thickness

(Approx. system thickness from 2 mm, without moisture barrier)

4 SUBSTRATE PREPARATION

- The concrete substrate must be sound and of sufficient compressive strength (minimum 25 N/mm²) with a minimum pull off strength of 1.5 N/mm²
- Prior to application, confirm substrate moisture content, relative humidity and dew point
- Must be not > 4% pbw moisture content. (Test method: Sika® Tramex meter or Standard Test method for indication of moisture in concrete by plastic sheet method according to ASTM D4263)
- Concrete substrates must be prepared mechanically using abrasive blast cleaning or scarifying equipment to remove cement laitance and achieve an open textured surface

- Weak concrete must be removed and surface defects such as blowholes and voids must be fully exposed
- All dust, loose and friable material must be completely removed from all surfaces before application of the product, preferably by brush and/or vacuum.
- If in doubt, apply a test area first.

5 APPLICATION

- Primer: Make sure that a continuous; pore free coat covers the substrate. If necessary, apply two priming coats.
- Wearing course: Sikafloor®-263 SL HC + Quartz sand are poured, spread evenly by means of a serrated trowel. Roll immediately in 2 directions with a spiked roller to ensure even thickness and to remove entrapped air.

LEGAL NOTE

The information, and, in particular, the recommendations relating to the application and end-use of Sika products, are given in good faith based on Sika's current knowledge and experience of the products when properly stored, handled and applied under normal conditions in accordance with Sika's recommendations. In practice, the differences in materials, substrates and actual site conditions are such that no warranty in respect of merchantability or of fitness for a particular purpose, nor any liability arising out of any legal relationship whatsoever, can be inferred either from this information, or from any written recommendations, or from any other advice offered. The user of the product must test the products suitability for the intended application and purpose. Sika reserves the right to change the properties of its products. The proprietary rights of third parties must be observed. All orders are accepted subject to our current terms of sale and delivery. Users must always refer to the most recent issue of the local Product Data Sheet for the product concerned, copies of which will be supplied on request.

Sika Limited (Vietnam)
 Nhon Trach 1 Industrial Zone
 Nhon Trach, Dong Nai
 Vietnam
 vnm.sika.com

Phone: (84-251) 3560 700
 Fax: (84-251) 3560 699
 Mail: sikavietnam@vn.sika.com

Method Statement
 Sikafloor®-263 SL – 2mm
 EDITION: 8/2018,